

## Origin of the Resistivity Anisotropy in the Nematic Phase of FeSe

M. A. Tanatar,<sup>1,2,\*</sup> A. E. Böhrer,<sup>1</sup> E. I. Timmons,<sup>1,2</sup> M. Schütt,<sup>3</sup> G. Drachuck,<sup>1,2</sup> V. Taufour,<sup>1</sup> K. Kothapalli,<sup>1,2</sup>  
A. Kreyssig,<sup>1,2</sup> S. L. Bud'ko,<sup>1,2</sup> P. C. Canfield,<sup>1,2</sup> R. M. Fernandes,<sup>3</sup> and R. Prozorov<sup>1,2,†</sup>

<sup>1</sup>Ames Laboratory, Ames, Iowa 50011, USA

<sup>2</sup>Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, USA

<sup>3</sup>School of Physics and Astronomy, University of Minnesota, Minneapolis, Minnesota 55455, USA

(Received 15 November 2015; published 16 September 2016)

The in-plane resistivity anisotropy is studied in strain-detwinned single crystals of FeSe. In contrast to other iron-based superconductors, FeSe does not develop long-range magnetic order below the tetragonal-to-orthorhombic transition at  $T_s \approx 90$  K. This allows for the disentanglement of the contributions to the resistivity anisotropy due to nematic and magnetic orders. Comparing direct transport and elastoresistivity measurements, we extract the intrinsic resistivity anisotropy of strain-free samples. The anisotropy peaks slightly below  $T_s$  and decreases to nearly zero on cooling down to the superconducting transition. This behavior is consistent with a scenario in which the in-plane resistivity anisotropy is dominated by inelastic scattering by anisotropic spin fluctuations.

DOI: 10.1103/PhysRevLett.117.127001

Electronic nematicity has emerged as a key concept in iron-based superconductors since the observation of in-plane resistivity anisotropy in stress-detwinned crystals of Co-doped BaFe<sub>2</sub>As<sub>2</sub> [1,2]. The fact that the resistivity anisotropy is much larger than what is expected from the small lattice distortion led to the proposal that the tetragonal-to-orthorhombic transition in the iron pnictides is driven not by phonons, but by an electronic nematic phase. Subsequent experiments revealed an intricate dependence of the resistivity anisotropy on doping (a sign change between electron- and hole-doped materials [2–6]), and disorder [7,8], sparking hot debates about its microscopic origins (see Refs. [9,10] for reviews).

Electronic contributions involved in the in-plane resistivity anisotropy [10] can be separated into the Drude weight and/or the scattering rate anisotropies. Fermi-surface anisotropies arising, for instance, from the ferro-orbital order triggered at the nematic transition affect mostly the Drude weight [11–13]. Anisotropic scattering can be due to elastic processes, such as the development of local magnetic order around an impurity [14,15], or inelastic processes, such as the scattering of electrons by anisotropic magnetic fluctuations [16,17] known to exist above  $T_s$  [18]. Recent stress-dependent optical reflectivity studies in Co-doped BaFe<sub>2</sub>As<sub>2</sub> point to a dominant effect of the Drude weight [19,20]. However, stripe magnetic order appearing at the magnetic transition severely complicates the analysis. This is because the magnetic state breaks translational symmetry leading to an anisotropic reconstruction of the Fermi surface [7,21] and to the appearance of “Dirac cones” [22], which may dramatically alter the resistivity anisotropy [23]. Disentangling these contributions is fundamental to reveal the origin of the resistivity anisotropy and, consequently, of the nematic state.

In this context, the stoichiometric FeSe [24] is an ideal system. It is rather clean (residual resistivity ratios as high as fifty [25]) and its tetragonal-to-orthorhombic phase transition at  $T_s \approx 90$  K is not accompanied by long-range magnetic order [26] eliminating effects of Fermi surface folding.

In this Letter we report the resistivity anisotropy measured in strain-detwinned single crystals of FeSe. Upon cooling, the anisotropy  $\Delta\rho(T) \equiv \rho_a - \rho_b$  ( $\rho_a$  and  $\rho_b$  are the resistivities along the orthorhombic  $a$  and  $b$  directions) initially increases, reaching a maximum at about 20 K below  $T_s$ , and then nearly vanishes upon further cooling towards the superconducting transition  $T_c \approx 8.5$  K. This pronounced nonmonotonic behavior is consistent with the scenario in which the main contributor to the resistivity anisotropy is inelastic scattering by magnetic fluctuations rather than the anisotropy of the elastic scattering or of the Fermi surface. To support this conclusion, we performed model calculations of resistivity anisotropy for the scattering of electrons by anisotropic magnetic fluctuations. We find that the anisotropy is well described by the product of two temperature-dependent functions,  $\Delta\rho(T) = \Upsilon(T)\phi(T)$ . The standard nematic order parameter  $\phi(T)$  increases upon cooling and the scattering function  $\Upsilon(T)$  decreases and vanishes as the temperature approaches zero.

Single crystals of FeSe ( $\sim 1$  mm<sup>2</sup> surface area and 20 to 150  $\mu\text{m}$  thick) were grown using chemical vapor transport as in Ref. [27,28]. Polarized light optical imaging [1,29] was used to characterize the orthorhombic domain pattern appearing below  $T_s$  as shown in Fig. 1. In the orthorhombic phase, the optical bireflectance is anisotropic, which permits visualization of domains of different orientations. Furthermore, the intensity of red, green, and blue (RGB) color components are directly related to the reflected

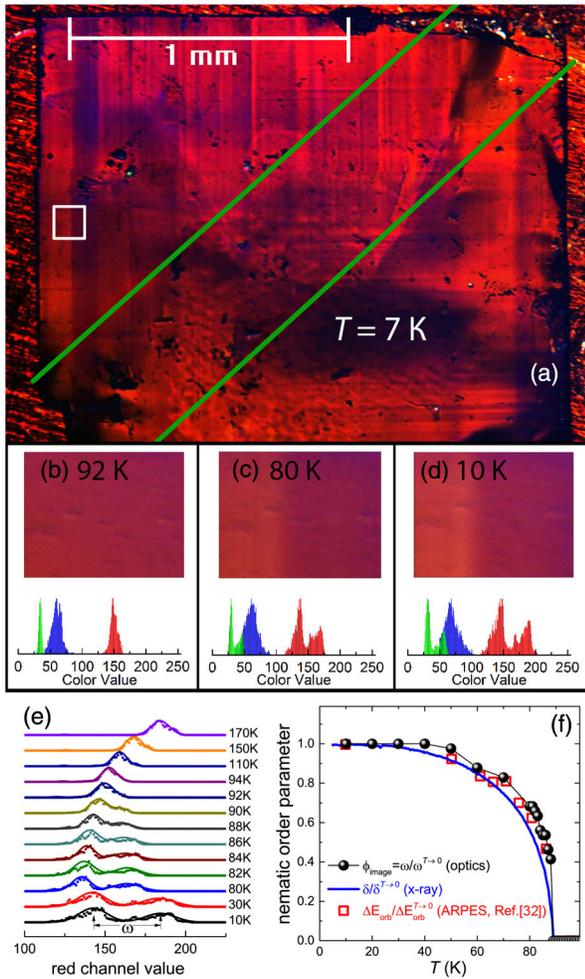


FIG. 1. (a) Polarized light image of an FeSe single crystal at 7 K, revealing orthorhombic domains oriented along the tetragonal [100] direction (parallel to the sample sides). For detwinning, the sample is cut along the [110] tetragonal direction as indicated by the green lines. Enlarged are the views of the area indicated by the white box in (a) and corresponding RGB histograms taken at (b) 92, (c) 80, and (d) 10 K. The change below  $T_s$  is most pronounced in the red channel (b)–(d) and the temperature evolution of its histograms is shown in panel (e). The peak splitting  $\omega$  was analyzed using a fit to two Gaussians [lines in (e)] and the normalized nematic order parameter,  $\phi_{\text{image}} = \omega(T)/\omega^{T \rightarrow 0}$ , is shown in panel (f) and compared with the results of angle-resolved photoemission spectroscopy (ARPES) measurements [32] and the orthorhombic lattice distortion  $\delta = (a - b)/(a + b)$  from our x-ray diffraction measurements.

photon frequency for a given color perception system [30]. Since different domains reflect polarized light differently, this allows extraction of the nematic order parameter. A similar analysis method was introduced in Ref. [31]. The intensity histograms of RGB channels in a clean area of the sample [white box in Fig. 1(a)] at different temperatures are shown in Figs. 1(b), 1(c), and 1(d). Above  $T_s$  the image is of uniform color, manifesting as single peaks in the histograms [panel (b)]. Below  $T_s$  the domains of different

colors lead to peak splitting in the histograms, most pronounced in the red channel [Figs. 1(c), 1(d)]. The temperature evolution of the red channel histogram is shown in panel (e). The peak splitting  $\omega$ , signaling the breaking of tetragonal symmetry, was determined using a fit to two Gaussians and its normalized value,  $\phi_{\text{image}}(T) \equiv \omega(T)/\omega^{T \rightarrow 0}$ , is shown in Fig. 1(f).  $\phi_{\text{image}}$  represents the optical reflectivity anisotropy and is a measure of the nematic order parameter by symmetry. Consistently, it agrees very well with the orthorhombic lattice distortion  $\delta = (a - b)/(a + b)$  determined by high-energy x-ray diffraction using measurements similar to those of Refs. [1,31], and the temperature dependence of a two-peak feature in energy dispersion curves observed by angle-resolved photoemission spectroscopy (ARPES) below  $T_N$  [32], see Fig. 1(f).

Samples for mechanical detwinning were cut along the tetragonal [110] direction, which becomes the orthorhombic  $a$  or  $b$  axis on cooling, as shown schematically by the green lines in Fig. 1(a). Tensile strain was applied to the sample through  $50 \mu\text{m}$  Ag wires also used as potential leads; see inset in Fig. 2(a). Wires for current contacts were mounted strain-free. All contacts were indium soldered. Figure 2(a) shows the resistivity of the FeSe sample measured in the strain-free twinned state  $\rho_t$ , and along the (longer)  $a$ -axis in the detwinned state achieved by application of tensile strain  $\epsilon_a$  of two different magnitudes  $\rho_a(\epsilon_1)$  and  $\rho_a(\epsilon_2)$ .  $\epsilon_a = \epsilon_1, \epsilon_2$  is controlled by pulling apart the arms of the horseshoe device. In the strain-free, twinned state  $\rho_t$  shows only a small kink at  $T_s$ . The sample is split into approximately equal areas of domains of two orientations, so its resistivity is  $\rho_t = (\rho_a + \rho_b)/2$ . Together with the measurements in detwinned samples, this allows us to extract the resistivity along the orthorhombic  $b$  axis  $\rho_b$ , and the in-plane anisotropy  $\Delta\rho$ , shown in Fig. 2(b) for the two strain values. The anisotropy increases markedly on cooling, evolves smoothly through  $T_s$ , and peaks below  $T_s$ . On further cooling it decreases, reaching small values at  $T_c$ . Note that  $\Delta\rho > 0$ , i.e., the resistivity is larger along the  $a$  direction, thus having the same sign as that of FeTe [33] and hole-doped  $\text{BaFe}_2\text{As}_2$  [4] and  $\text{Ca}_{1-x}\text{Na}_x\text{Fe}_2\text{As}_2$  [5] compounds, and opposite to electron-doped and isovalently substituted  $\text{BaFe}_2\text{As}_2$  [1,2,34].

The application of strain not only promotes the formation of orthorhombic domains of only one orientation below  $T_s$ , but it also induces resistivity anisotropy above and below  $T_s$  due to the elastoresistivity of the material. Figure 3(a) shows the elastoresistivity coefficients  $2m_{66}$  and  $m_{11} - m_{12}$  measured using a piezo-based setup, similar to that described in Refs. [35,36]. Samples of approximate dimensions  $1 \times 0.3 \times 0.07 \text{ mm}^3$  were glued to one side of a piezostack, shown in the left inset in Fig. 3(a). The change of sample resistance was measured as a function of anisotropic strain, monitored *in situ* using crossed strain gauges glued to the opposite side of the piezostack. The

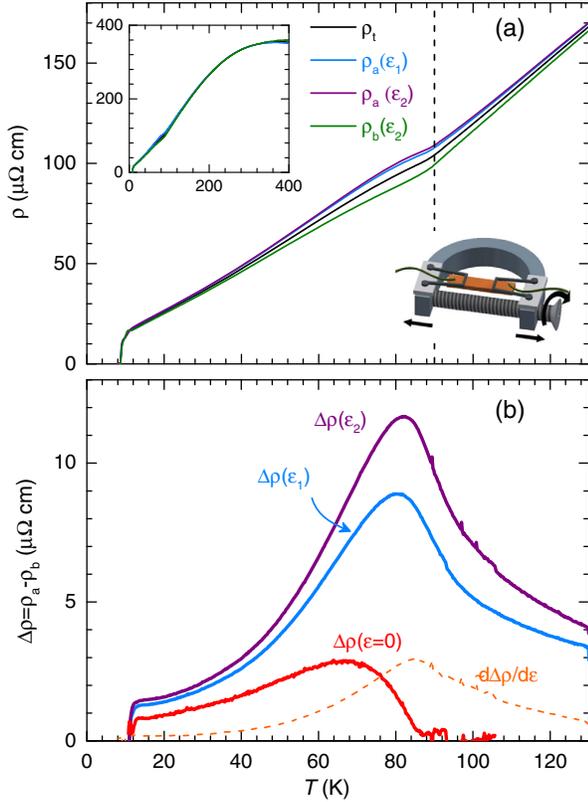


FIG. 2. (a) Temperature-dependent resistivity of FeSe measured in a free-standing state,  $\rho_t$  (black curve), and under two values of uniaxial tensile strain,  $\varepsilon_a = \varepsilon_1, \varepsilon_2$ , representing a fully detwinned state,  $\rho_a$  (blue and purple curves). The resistivity along the orthorhombic  $b$  direction was calculated as  $\rho_b = 2\rho_t - \rho_a$  (green curve). The insets show the whole temperature range and the schematics of the horseshoe detwinning device. (b) Resistivity anisotropy  $\Delta\rho \equiv \rho_a - \rho_b$  for the two values of strain,  $\varepsilon_1$  and  $\varepsilon_2$ . Their difference  $\Delta\rho(\varepsilon_1) - \Delta\rho(\varepsilon_2)$  is proportional to the strain-derivative  $d\Delta\rho/d\varepsilon_a$  (dashed orange line). The latter was used to extract the intrinsic (strain-free) in-plane anisotropy of the resistivity  $\Delta\rho(\varepsilon_a = 0) \approx \Delta\rho(\varepsilon_2) - (d\Delta\rho/d\varepsilon_a)\varepsilon_2$  in the orthorhombic phase (red line).

elastoresistivity coefficient  $2m_{66}$  corresponds to the normalized derivative of  $\Delta\rho$  with respect to the orthorhombic shear strain  $\varepsilon_a - \varepsilon_b$ ,  $2m_{66} = 1/\rho[d\Delta\rho/d(\varepsilon_a - \varepsilon_b)]$  [36]. It clearly diverges on approaching  $T_s$  from above [Fig. 3(a)], following almost perfectly a Curie-Weiss law,  $2m_{66} \sim 1/(T - T_0)$  with  $T_0 \approx 83$  K [right inset in Fig. 3(a)], in qualitative agreement with a previous report [32]. A second elastoresistivity mode,  $m_{11} - m_{12}$ , is related to the derivative of the resistivity anisotropy between two diagonals of the orthorhombic unit cell,  $[110]_o$  and  $[1\bar{1}0]_o$ , with respect to the corresponding shear strain,  $m_{11} - m_{12} = 1/\rho\{[d(\rho_{[110]_o} - \rho_{[1\bar{1}0]_o})]/[d(\varepsilon_{[110]_o} - \varepsilon_{[1\bar{1}0]_o})]\}$  [36]. This mode does not couple to the nematic order parameter and is, as expected, found to be almost zero above  $T_s$ .

In the strain-free samples,  $\Delta\rho = 0$  is expected for  $T > T_s$  and the observed finite resistivity anisotropy is

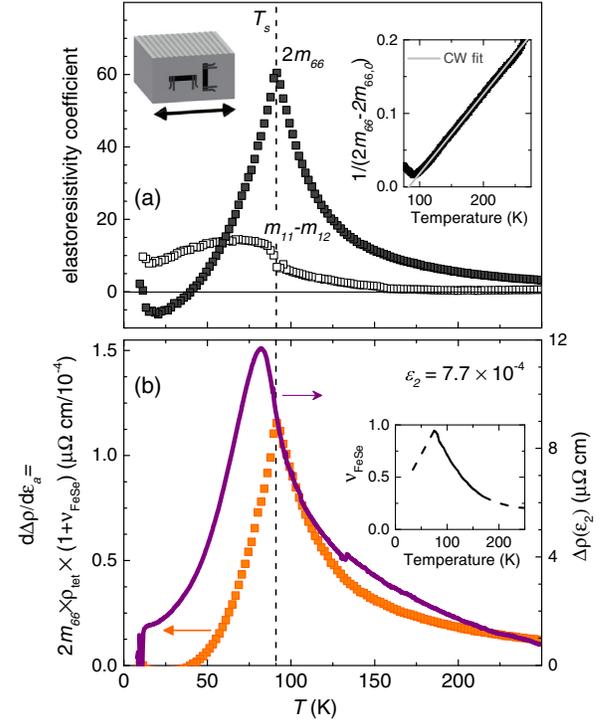


FIG. 3. (a) Elastoresistivity coefficients  $2m_{66}$  and  $m_{11} - m_{12}$  of FeSe measured using crossed samples glued to a piezostack, shown schematically in the left inset. The right inset shows the inverse of  $2m_{66} - 2m_{66,0}$  demonstrating nearly perfect Curie-Weiss-like behavior,  $2m_{66} = A/(T - T_0) + 2m_{66,0}$  with  $2m_{66,0} = -2.6$  and  $T_0 = 83$  K. (b) Scaling of  $2m_{66} = 1/\rho_t[d\Delta\rho/d(\varepsilon_a - \varepsilon_b)]$  with the resistivity anisotropy  $\Delta\rho(\varepsilon_2)$  measured in detwinned samples. Here, we assume that  $\Delta\rho(\varepsilon_2)$  is induced by the applied strain above  $T_s$ , so that  $\Delta\rho(\varepsilon_2) = \varepsilon_2(d\Delta\rho/d\varepsilon_a)$  and use the identity  $d(\varepsilon_a - \varepsilon_b)/d\varepsilon_a = 1 + \nu_{\text{FeSe}}$  to transform between the two quantities. The inset shows the Poisson ratio of FeSe,  $\nu_{\text{FeSe}}$ , determined from the ultrasound data of Ref. [37] (solid line), and extrapolated to 250 K and below  $T_s$  (dashed lines).

likely a consequence of the applied strain. We therefore compare in Fig. 3(b) the resistivity anisotropy under applied strain  $\varepsilon_2$ , given in this case by  $\Delta\rho(\varepsilon_2) = \varepsilon_2(d\Delta\rho/d\varepsilon_a)$ , with the elastoresistivity data. Because  $2m_{66} = 1/\rho[d\Delta\rho/d(\varepsilon_a - \varepsilon_b)]$ , we use the identity  $[d(\varepsilon_a - \varepsilon_b)/d\varepsilon_a] = 1 + \nu_{\text{FeSe}}$  to transform between strain derivatives. Here,  $\nu_{\text{FeSe}}$  is the Poisson ratio of FeSe calculated from ultrasound data [37]. Clearly,  $\Delta\rho(\varepsilon_2)$  and  $2m_{66}\rho_t(1 + \nu_{\text{FeSe}}) = d\Delta\rho/d\varepsilon_a$  behave similarly for  $T > T_s$ , explaining the experimentally observed tail of  $\Delta\rho$  above  $T_s$ . The scaling yields  $\varepsilon_2 = 7.7 \times 10^{-4}$  ( $\sim 40\%$  of the distortion in the orthorhombic phase) for the external strain applied through the horseshoe device. Below  $T_s$ , samples in the elastoresistivity setup are not fully detwinned, so that the domains dominate the measured  $m_{66}$ , which prohibits such a comparison.

To determine the effect of strain on the resistivity below  $T_s$ , in Fig. 2(b) we return to the resistivity curves in a fully

detwinned state obtained for two constant strains,  $\rho_a(\varepsilon_1)$  and  $\rho_a(\varepsilon_2)$ . In the linear response regime, we can approximate  $d\Delta\rho/d\varepsilon_1 \approx [\Delta\rho(\varepsilon_1) - \Delta\rho(\varepsilon_2)]/(\varepsilon_1 - \varepsilon_2)$ . The derivative is used to extract the intrinsic resistivity anisotropy in the absence of external strain,  $\Delta\rho(\varepsilon \rightarrow 0) \approx \Delta\rho(\varepsilon_2) - \varepsilon_2[\Delta\rho(\varepsilon_2) - \Delta\rho(\varepsilon_1)]/(\varepsilon_2 - \varepsilon_1)$ . The constant value of  $\varepsilon_2/(\varepsilon_2 - \varepsilon_1) \approx 3.7$  is fixed by enforcing  $\Delta\rho(\varepsilon = 0) = 0$  in the tetragonal state. The resulting  $\Delta\rho(\varepsilon = 0)$  [red line in Fig. 2(b)] clearly displays a broad maximum 20 K below  $T_s$ .

The previous comparison between  $m_{66}$  and  $\Delta\rho$  reveals that, above  $T_s$ , the resistivity anisotropy is proportional to the strain, and, therefore, to the nematic order parameter  $\phi$ . A similar behavior was experimentally observed in the iron pnictides [31]. This relationship indeed is more general: because  $\Delta\rho$  and  $\phi$  break the same symmetry, they are generally proportional to each other, i.e.,  $\Delta\rho = \Upsilon\phi$ , where  $\Upsilon$  is the proportionality factor [35,38]. It is clear from Fig. 1 that  $\phi$  displays a standard order-parameter behavior, monotonically increasing upon cooling. In contrast, the resistivity anisotropy  $\Delta\rho$  shows a pronounced peak below  $T_s$  and decreases to nearly zero at  $T \rightarrow 0$ . This behavior must therefore arise from the temperature dependence of the proportionality factor  $\Upsilon$  that should also vanish as  $T \rightarrow 0$ , since  $\phi$  remains finite and large at  $T \rightarrow 0$ . Among the possible microscopic contributions to  $\Delta\rho$  affecting  $\Upsilon$ —anisotropies of Fermi surface, elastic, and inelastic scattering rates, only the latter one naturally leads to the observed behavior. Phenomenologically, this is nicely illustrated by using  $\phi_{\text{image}}$  of Fig. 1 as a proxy of  $\phi$ , and the resistivity of the twinned sample  $\rho_t(T)$  as a proxy of  $\Upsilon$ . The latter relies on the assumption that the inelastic scattering also dominates the isotropic transport properties. Indeed, the product  $\phi_{\text{image}}(T)\rho_t(T)$ , shown by the black symbols in Fig. 4, captures much of the temperature dependence of  $\Delta\rho(T)$ .

In order to develop a microscopic scenario for this behavior, we consider the three-band model of Ref. [16], in which electrons are scattered by magnetic fluctuations. This model contains one circular hole pocket at the center of the Brillouin zone, with dispersion  $\varepsilon_{h,\mathbf{k}} = \varepsilon_h - k^2/2m$ , and two electron pockets centered at momenta  $\mathbf{Q}_1 = (\pi, 0)$ ,  $\varepsilon_{e_1,\mathbf{k}+\mathbf{Q}_1} = -\varepsilon_e + k_x^2/2m_x + k_y^2/2m_y$ , and  $\mathbf{Q}_2 = (0, \pi)$ ,  $\varepsilon_{e_2,\mathbf{k}+\mathbf{Q}_2} = -\varepsilon_e + k_x^2/2m_y + k_y^2/2m_x$ . Below  $T_s$ , the onset of nematic order leads to stronger fluctuations at the ordering vector  $\mathbf{Q}_1$  than at  $\mathbf{Q}_2$ , a behavior observed experimentally by neutron scattering [18]. Depending on the relative positions  $\mathbf{k}_{hs}$  of the hot spots—points of the hole and electron pockets connected by the ordering vectors,  $\varepsilon_{h,\mathbf{k}_{hs}} = \varepsilon_{e_1,\mathbf{k}_{hs}+\mathbf{Q}_1} = 0$ —one finds  $\rho_a > \rho_b$  or  $\rho_b > \rho_a$  (see also Ref. [17]). Indeed, the change in the positions of the hot spots from hole doping to electron doping was argued in Ref. [4] as a possible reason for the sign change of  $\Delta\rho$ . Whether the hot spot positions in FeSe are consistent with the observed  $\rho_a > \rho_b$  requires detailed ARPES

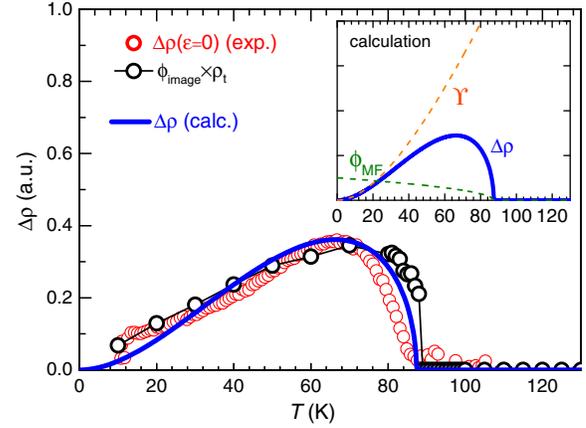


FIG. 4. Experimental temperature-dependent resistivity anisotropy in the zero-strain limit [from Fig. 2(b), red symbols],  $\Delta\rho(T)$ , compared to the product of the temperature-dependent experimentally determined order parameter  $\phi_{\text{image}}$  of Fig. 1(g) and the isotropic resistivity  $\rho_t$  of Fig. 2(a) (black circles). The blue line shows the results of a model calculation where  $\Delta\rho$  is determined by the product of a mean-field-type nematic order parameter  $\phi(T)$  and a temperature dependent function  $\Upsilon(T)$  resulting from inelastic scattering promoted by spin fluctuations (see inset).

measurements above  $T_s$ . Using the formalism developed in Ref. [16], we perform an expansion of the resistivity anisotropy, finding  $\Delta\rho = \Upsilon\phi$ . Here, we assume  $\phi(T)$  to display a mean-field-like behavior  $\phi(T) = \phi_0\sqrt{1 - T/T_s}$ . The proportionality constant  $\Upsilon$ , arising from the scattering of electrons by magnetic excitations, depends on the magnetic correlation length  $\xi$  and on the Landau damping of the magnetic fluctuations  $\Gamma$ . In particular, we find  $\Upsilon = \Upsilon_0 T(1 + 3\Gamma\xi^{-2}/2\pi T)^{-1}$ , where  $\Upsilon_0$  is a constant that depends on the geometry of the Fermi surface and on the residual resistivity. This leads to  $\Upsilon(T \rightarrow 0) \sim T^2$  and, therefore, the different temperature dependencies of  $\phi(T)$  and  $\Upsilon(T)$  give rise to a maximum in  $\Delta\rho$  below  $T_s$ . This behavior is illustrated in Fig. 4, where we plot the calculated  $\Delta\rho$  for  $\xi = 3a$  and  $\Gamma = 150$  meV (the product  $\phi_0\Upsilon_0$  is treated as a fitting parameter to the data). Note that  $\xi$  was assumed to be small and temperature independent above  $T_s$ , in agreement with NMR data [39,40]. Below  $T_s$ , the onset of nematic order renormalizes  $\xi$  and leads to its enhancement [41], as observed in the same NMR data. The good agreement between the calculated and the measured  $\Delta\rho$  suggests that the inelastic scattering by anisotropic magnetic fluctuations can explain the experimentally observed nonmonotonic temperature-dependence of the in-plane resistivity anisotropy.

In conclusion, the comparison of direct transport and elastoresistivity measurements in FeSe was used to extract the intrinsic in-plane resistivity anisotropy of strain-free samples. A strong non-monotonic temperature dependence, displaying a maximum below  $T_s$  and becoming very small

as  $T \rightarrow 0$  was observed. This behavior is explained by anisotropic inelastic scattering as a main contribution to  $\Delta\rho$ , shedding new light on the origin of nematicity in FeSe. Since the superconducting state in this compound emerges from a nematic-paramagnetic state, the observed connection between nematicity and inelastic magnetic fluctuations provides an important ingredient for modeling the pairing mechanism in FeSe.

We thank V.G. Kogan for useful discussions and A. Sapkota, W.T. Jayasekara, B.G. Ueland, and A.I. Goldman for support of the x-ray diffraction measurement. This work was supported by the U.S. Department of Energy (DOE), Office of Science, Basic Energy Sciences, Materials Science and Engineering Division. The experimental research was performed at Ames Laboratory, which is operated for the U.S. DOE by Iowa State University under Contract No. DE-AC02-07CH11358, and also used resources at the Advanced Photon Source, a U.S. DOE, Office of Science User Facility, operated by Argonne National Laboratory under No. DE-AC02-06CH11357. The theoretical part (R. M. F.) was supported by U.S. DOE under Award No. DE-SC0012336. M.S. acknowledges the support from the Humboldt Foundation. G.D. was funded by the Gordon and Betty Moore Foundation's EPIQS Initiative through Grant No. GBMF4411.

*Note added in the proof*—Recent ARPES experiments [32,42] have challenged the identification of the ARPES splitting reproduced in our Fig. 1(f) as the  $d_{xz}/d_{yz}$  orbital splitting proposed by other groups [43,44]. While this issue remains unsettled, its outcome does not affect the conclusions of our study.

\*tanatar@ameslab.gov

†prozorov@ameslab.gov

- [1] M. A. Tanatar, E. C. Blomberg, A. Kreyssig, M. G. Kim, N. Ni, A. Thaler, S. L. Bud'ko, P. C. Canfield, A. I. Goldman, I. I. Mazin, and R. Prozorov, *Phys. Rev. B* **81**, 184508 (2010).
- [2] J.-H. Chu, J. G. Analytis, K. D. Greve, P. L. McMahon, Z. Islam, Y. Yamamoto, and I. R. Fisher, *Science* **329**, 824 (2010).
- [3] J. J. Ying, X. F. Wang, T. Wu, Z. J. Xiang, R. H. Liu, Y. J. Yan, A. F. Wang, M. Zhang, G. J. Ye, P. Cheng, J. P. Hu, and X. H. Chen, *Phys. Rev. Lett.* **107**, 067001 (2011).
- [4] E. C. Blomberg, M. A. Tanatar, R. M. Fernandes, I. I. Mazin, B. Shen, H.-H. Wen, M. D. Johannes, J. Schmalian, and R. Prozorov, *Nat. Commun.* **4**, 1914 (2013).
- [5] J. Q. Ma, X. G. Luo, P. Cheng, N. Zhu, D. Y. Liu, F. Chen, J. J. Ying, A. F. Wang, X. F. Lu, B. Lei, and X. H. Chen, *Phys. Rev. B* **89**, 174512 (2014).
- [6] T. Kobayashi, K. Tanaka, S. Miyasaka, and Setsuko Tajima, *J. Phys. Soc. Jpn.* **84**, 094707 (2015).
- [7] T. Terashima, N. Kurita, M. Tomita, K. Kihou, C.-H. Lee, Y. Tomioka, T. Ito, A. Iyo, H. Eisaki, T. Liang, M. Nakajima, S. Ishida, S.-i. Uchida, H. Harima, and S. Uji, *Phys. Rev. Lett.* **107**, 176402 (2011).
- [8] H.-H. Kuo and I. R. Fisher, *Phys. Rev. Lett.* **112**, 227001 (2014).
- [9] I. R. Fisher, L. Degiorgi, and Z. X. Shen, *Rep. Prog. Phys.* **74**, 124506 (2011).
- [10] R. M. Fernandes, A. V. Chubukov, and J. Schmalian, *Nat. Phys.* **10**, 97 (2014).
- [11] C.-C. Chen, J. Maciejko, A. P. Sorini, B. Moritz, R. R. P. Singh, and T. P. Devereaux, *Phys. Rev. B* **82**, 100504 (2010).
- [12] W. Lv and P. Phillips, *Phys. Rev. B* **84**, 174512 (2011).
- [13] S. Liang, G. Alvarez, C. Sen, A. Moreo, and E. Dagotto, *Phys. Rev. Lett.* **109**, 047001 (2012).
- [14] M. P. Allan, T.-M. Chuang, F. Massee, Yang Xie, N. Ni, S. L. Bud'ko, G. S. Boebinger, Q. Wang, D. S. Dessau, P. C. Canfield, M. S. Golden, and J. C. Davis, *Nat. Phys.* **9**, 220 (2013).
- [15] M. N. Gastiasoro, I. Paul, Y. Wang, P. J. Hirschfeld, and B. M. Andersen, *Phys. Rev. Lett.* **113**, 127001 (2014).
- [16] R. M. Fernandes, E. Abrahams, and J. Schmalian, *Phys. Rev. Lett.* **107**, 217002 (2011).
- [17] M. Breitzkreuz, P. M. R. Brydon, and C. Timm, *Phys. Rev. B* **90**, 121104(R) (2014).
- [18] X. Lu, J. T. Park, R. Zhang, H. Luo, A. H. Nevidomskyy, Q. Si, and P. Dai, *Science* **345**, 657 (2014).
- [19] C. Mirri, A. Dusza, S. Bastelberger, J.-H. Chu, H.-H. Kuo, I. R. Fisher, and L. Degiorgi, *Phys. Rev. B* **90**, 155125 (2014).
- [20] C. Mirri, A. Dusza, S. Bastelberger, M. Chinotti, L. Degiorgi, J.-H. Chu, H.-H. Kuo, and I. R. Fisher, *Phys. Rev. Lett.* **115**, 107001 (2015).
- [21] B. Valenzuela, E. Bascones, and M. J. Calderon, *Phys. Rev. Lett.* **105**, 207202 (2010).
- [22] K. K. Huynh, Y. Tanabe, and K. Tanigaki, *Phys. Rev. Lett.* **106**, 217004 (2011).
- [23] H.-H. Kuo, J.-H. Chu, S. C. Riggs, L. Yu, P. L. McMahon, K. D. Greve, Y. Yamamoto, J. G. Analytis, and I. R. Fisher, *Phys. Rev. B* **84**, 054540 (2011).
- [24] F.-C. Hsu, J.-Y. Luo, K.-W. Yeh, T.-K. Chen, T.-W. Huang, P. M. Wu, Y.-C. Lee, Y.-L. Huang, Y.-Y. Chu, D.-C. Yan, and M.-K. Wu, *Proc. Natl. Acad. Sci. U.S.A.* **105**, 14262 (2008).
- [25] S. Kasahara, T. Watashige, T. Hanaguri, Y. Kohsaka, T. Yamashita, Y. Shimoyama, Y. Mizukami, R. Endo, H. Ikeda, K. Aoyama, T. Terashima, S. Uji, T. Wolf, H. von Löhneysen, T. Shibauchi, and Y. Matsuda, *Proc. Natl. Acad. Sci. U.S.A.* **111**, 16309 (2014).
- [26] T. M. McQueen, A. J. Williams, P. W. Stephens, J. Tao, Y. Zhu, V. Ksenofontov, F. Casper, C. Felser, and R. J. Cava, *Phys. Rev. Lett.* **103**, 057002 (2009).
- [27] A. E. Böhmer, F. Hardy, F. Eilers, D. Ernst, P. Adelman, P. Schweiss, T. Wolf, and C. Meingast, *Phys. Rev. B* **87**, 180505 (2013).
- [28] A. E. Böhmer, V. Taufour, W. E. Straszheim, T. Wolf, and P. C. Canfield, *Phys. Rev. B* **94**, 024526 (2016).
- [29] M. A. Tanatar, A. Kreyssig, S. Nandi, N. Ni, S. L. Bud'ko, P. C. Canfield, A. I. Goldman, and R. Prozorov, *Phys. Rev. B* **79**, 180508(R) (2009).
- [30] A. S. Glassner, *IEEE Comput. Graph. Appl.* **9**, 95 (1989).
- [31] E. C. Blomberg, A. Kreyssig, M. A. Tanatar, R. M. Fernandes, M. G. Kim, A. Thaler, J. Schmalian, S. L.

- Bud'ko, P. C. Canfield, A. I. Goldman, and R. Prozorov, *Phys. Rev. B* **85**, 144509 (2012).
- [32] M. D. Watson, T. K. Kim, A. A. Haghighirad, N. R. Davies, A. McCollam, A. Narayanan, S. F. Blake, Y. L. Chen, S. Ghannadzadeh, A. J. Schofield, M. Hoesch, C. Meingast, T. Wolf, and A. I. Coldea, *Phys. Rev. B* **91**, 155106 (2015).
- [33] Juan Jiang, C. He, Y. Zhang, M. Xu, Q. Q. Ge, Z. R. Ye, F. Chen, B. P. Xie, and D. L. Feng, *Phys. Rev. B* **88**, 115130 (2013).
- [34] H.-H. Kuo, James G. Analytis, J.-H. Chu, R. M. Fernandes, J. Schmalian, and I. R. Fisher, *Phys. Rev. B* **86**, 134507 (2012).
- [35] J.-H. Chu, H.-H. Kuo, J. G. Analytis, and I. R. Fisher, *Science* **337**, 710 (2012).
- [36] Hsueh-Hui Kuo, Maxwell C. Shapiro, Scott C. Riggs, and Ian R. Fisher, *Phys. Rev. B* **88**, 085113 (2013).
- [37] G. A. Zvyagina, T. N. Gaydamak, K. R. Zhekov, I. V. Bilich, V. D. Fil, D. A. Chareev, and A. N. Vasiliev, *Europhys. Lett.* **101**, 56005 (2013).
- [38] M. Schütt and R. M. Fernandes, *Phys. Rev. Lett.* **115**, 027005 (2015).
- [39] A. E. Böhmer, T. Arai, F. Hardy, T. Hattori, T. Iye, T. Wolf, H. v. Löhneysen, K. Ishida, and C. Meingast, *Phys. Rev. Lett.* **114**, 027001 (2015).
- [40] S. H. Baek, D. V. Efremov, J. M. Ok, J. S. Kim, J. van den Brink, and B. Büchner, *Nat. Mater.* **14**, 210 (2015).
- [41] Q. Zhang, R. M. Fernandes, J. Lamsal, J. Yan, S. Chi, G. S. Tucker, D. K. Pratt, J. W. Lynn, R. W. McCallum, P. C. Canfield, T. A. Lograsso, A. I. Goldman, D. Vaknin, and R. J. McQueeney, *Phys. Rev. Lett.* **114**, 057001 (2015).
- [42] A. Fedorov, A. Yaresko, T. K. Kim, E. Kushnirenko, E. Haubold, T. Wolf, M. Hoesch, A. Grueneis, B. Buechner, and S. V. Borisenko, *arXiv:1606.03022*.
- [43] T. Shimojima *et al.*, *Phys. Rev. B* **90**, 121111(R) (2014).
- [44] P. Zhang *et al.*, *Phys. Rev. B* **91**, 214503 (2015).